

GARNET TEST REPORT


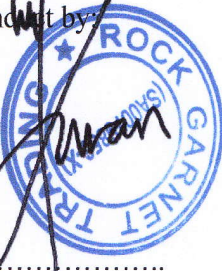
STANDARD	SA 2.5
METHOD	MANUAL BLASTING
SUBSTRATE	CARBON STEEL
PROJECT TITLE	TOPSIDE CONSTRUCTION & MAINTENANCE SERVICES
CLIENT/OWNER	Carigali Hess
SUPPLIER	ROCK GARNET TRADING SDN. BHD
TEST LOCATION / YARD	KSB KEMAMAN
PERSON PRESENT	Mr.Kumaran, Mr Ahmad Affendy,
DATE OF TEST	29 th March 2012.
GARNET TYPE	RGT SUPREME GARNET, 30/60 MESH

TEST RESULTS


INSPECTION CRITERIA	OBSERVATION		REMARKS
	REQUIRED	ACTUAL	
GARNET SIZE	30/60	30/60	ACCEPTABLE
CLEANLINESS	Sa2.5	Sa 2.5	ACCEPTABLE
DUST LEVEL	Level 0-3	Level 1	ACCEPTABLE
SOLUBLE WATER TEST/ DISCOLORATION	Clean and clear	Clean and clear	ACCEPTABLE
RESIDUE/GREASE/OIL	Shall not contain	Does not contain	ACCEPTABLE
SURFACE PROFILE – 01	40~70µm	54µm , 54µm , 56µm , 52 µm , 52µm , 40µm 64µm = AV:53µm	ACCEPTABLE
SURFACE PROFILE – 02	40~70µm	42 µm , 60µm , 52 µm , 62 µm , 52µm , 64 µm , =AV:58µm	ACCEPTABLE

Notes:

- 1) Acceptance surface profile 40~70µm (micron) for external.
- 2) Test area taken randomly and the results serve as a guide only owing to contraction and distribution of chloride may not be uniform throughout the substrates.
- 3) This test report is prepared on the inspection made as the above date and from our best knowledge, it is issued without prejudice.

Conducted by: 


Witnessed by:



.....
 Carigali Hess
 Mr. Ismail

Witnessed by:


 JOTUN (M) SDN BHD
 Doc Reviewed
 Verification
 IRWINZAM
 Senior Coating Advisor

.....
 Jotun Malaysia Sdn bhd
 Mr. Irwinzam

Witnessed by:




.....
 Pioneer Engineering Sdn Bhd
 Mr. Ahmad Affendy Mohd Ayob

.....
 Rock Garnet Trading Sdn Bhd
 Mr. Kumaran